

NASA Contractor Report 3370

NASA
CR
3370
c.1

A Study of Crystal Growth by Solution Technique

R. B. Lal

GRANT NSG-8033
JANUARY 1981

NASA

LOAN COPY
AFWL TECHN
KIRTLAND AFB

0061955

TECH LIBRARY KAFB, NM



NASA Contractor Report 3370

A Study of Crystal Growth by Solution Technique

R. B. Lal

*Alabama Agriculture and Mechanical University
Huntsville, Alabama*

Prepared for
Marshall Space Flight Center
under Grant NSG-8033



National Aeronautics
and Space Administration

**Scientific and Technical
Information Branch**

1981

FOREWORD

This report deals with work done under NASA Grant NSG-8033 to the Alabama A&M University (AAMU) in Huntsville, Alabama. The work reported here was done under the technical supervision of Mr. Charles Schafer of NASA/MSFC, Fluid Dynamics Branch, Atmospheric Sciences Division, Space Sciences Laboratory, and his cooperation and comments are gratefully acknowledged.

The author thanks the NASA Office of University Affairs for the award of this grant which evolved into a flight experiment for the SL 3 Mission. The author also thanks Dr. Leon Frazier, Dr. Bessie W. Jones, and Dr. M. G. George (all of AAMU) for their continued interest and support during the progress of this work.

TABLE OF CONTENTS

	Page
I. INTRODUCTION	1
II. OBJECTIVES	3
III. BACKGROUND	4
IV. CRYSTAL GROWTH FROM SOLUTION	5
IV. 1. Advantage of Growth from Solution	5
IV. 2. Effect of Impurity Adsorption on Kinetics of Crystal Growth from Solution	9
IV. 3. Uncertainties Regarding Crystal Growth in Low Gravity Environment	10
V. EXPERIMENTAL PROCEDURE	11
V. 1. Test of Thermal Stability of the System	16
V. 2. Growth of TGS Crystals	17
V. 3. Evaluation Plan	19
VI. ADDITIONAL TASKS UNDER THE GRANT	20
REFERENCES	21
BIBLIOGRAPHY	22

I. INTRODUCTION

The promise shown by the results of Skylab I and II and the ASTP experiments,^{1,2} on materials science are in confirmation of the possibility of processing of materials in space on a routine basis. These results have logically placed an emphasis on simple crystal systems. The results of different flight experiments on various missions have shown excellent promise and have prompted a closer look at the opportunities for more complex and more valuable compound materials.

The NASA materials processing in space (MPS) program is intended to develop applications of space flights in materials science and technology, including both research and manufacturing activities. Its initial goal is to demonstrate the value of space for materials work by achieving significant scientific results and/or developing specific useful materials and products.

Many technologies are dependent on single crystal materials to varying degree. The materials can be processed for making efficient semi-conductors for use in the field of communications, materials which will make better super-conductors for control and distribution of energy, materials for energy conversion devices, materials for various kinds of detectors, and materials for non-linear optical devices. The eventual processing of materials in space is likely to become a major reality with the operational space shuttle in the 80's.

The advantages of weightless environment for materials processing include: a) absence of buoyant convection, b) absence of density segregation, c) absence of sagging, and d) opportunities of containerless processing. With regard to the growth of crystals, the primary advantage is the absence of buoyant convection. A growing crystal extracts materials from and/or releases heat into the surrounding fluid, thereby lowering the fluid's density. So on earth under 1-g conditions, a growing crystal is surrounded by a rising convection current. In most cases, this convection is unstable and gives rise to growth rate instabilities which cause impurity distribution fluctuations and defects such as fluid inclusions.³⁻⁷

It would, therefore, be expected that crystals grown in low-gravity environment would be more uniform in composition and have fewer defects than their one-g counterparts.

II. OBJECTIVES

The objective of this investigation is to study the mechanism of crystal growth by the solution technique with special reference to materials for electro-optical devices.

During this investigation, a flight experiment entitled, "Solution Growth of Crystals in 0-Gravity," was proposed to NASA. The proposal was accepted by NASA in September 1977, and the experiment is now approved for flight on the SL-3 mission under a separate NASA contract.

III. BACKGROUND

In recent years, new applications for non-linear optical devices have been found for ferroelectric single crystals such as Triglycine Sulfate (TGS) $(\text{NH}_2\text{CH}_2\text{COOH})_3 \text{H}_2\text{SO}_4$, crystals of iodate family and others. Single crystals of TGS may be used for infra-red image parametric up-conversion due to their phase match ability and for image tubes for television displays of thermal scenes using their large pyroelectric effect. There is, also, an increasing interest in detectors requiring less cooling or no cooling at all, even if they have low performance, which may lead to systems with greater cost-effectiveness. However, the undisturbed operation of these devices and techniques requires single crystals of high optical quality, i.e., of high purity, high homogeneity concerning the physical properties, low density of structural defects and free from inclusions and strains. The long-duration orbital flights in the space shuttle era will definitely allow growth of these crystals using solution technique.

IV. CRYSTAL GROWTH FROM SOLUTION

Crystal growth from solutions is simple in principle and has many applications. The technique is particularly useful for growth of materials which have high vapor pressure or decompose irreversibly at the melting point. Crystals will be grown from solution if the solution is supersaturated, i.e. it contains more solute than it can hold in equilibrium with the solid. The growth methods⁸, are based on solvent used, because the equipment, range application, problems and approach are to a large extent determined by the choice of the solvent. However, the more fundamental delineation of the methods could be made on the basis of the methods of producing supersaturation. The growth methods can be divided on this basis.

1. Isothermal methods (constant temperature methods)
 - A. Solvent evaporation or solvent concentration change (mainly used in aqueous and molten salt growth)
 - B. Temperature differential (mainly used in hydrothermal, aqueous and molten salt growth; also includes temperature-gradient zone melting when the gradient is moved through the sample).
 - C. Chemical or electrochemical reaction (mainly used in aqueous growth)
2. Non-isothermal methods (temperature variation methods)
 - A. Slow cooling (mainly used in aqueous, liquid metal solvent, and molten-salt growth)
 - B. Temperature-gradient zone melting (when the gradient is imposed over the whole sample).

IV. 1. Advantages of Growth from Solution

In general solution growth can be accomplished at temperatures considerably below the melting point of the material, and the use of lower temperature alleviates many of the problems associated with the melt growth process.

The main advantages are listed below.

- 1) The most important advantage of crystal growth from solution is the control that it provides over the temperature of growth. This makes it possible to grow crystals that are unstable at their melting points or that exist in several crystal forms depending upon temperature.
- 2) A second advantage is the control of viscosity, thus permitting crystals that tend to form glasses when cooled from melts to be grown.
- 3) Crystals grown from solution usually have well-defined faces as compared with those from melts.
- 4) It avoids strains, reduces vacancy concentration, and sometime reduces dislocations and low angle grain boundaries associated with high temperature growth.
- 5) Solution growth or low temperature growth is experimentally more convenient. Higher temperature processes are often more demanding on equipment and difficult to control, and harder to keep clean so that products are pure.

Solution growth has had its main success in the preparation of bulk crystals.

There are some disadvantages of a polycomponent growth and they are enumerated below.

- 1) The additional component will be contaminant and will have solid stability in the grown crystal.
- 2) Elimination of the additional component at the growing interface will set an upper limit on rate of growth. Diffusion will be important in this process. This may be an advantage in low-gravity and will be a dominant factor.
- 3) Because of the concentration gradient at the growing interface, constitutional supercooling will often occur; facets effects, cellular growth and dendritic growth can thus be problems.

The process of crystallization involves simultaneous mass and heat transport between the crystal surface and the surrounding fluid. In almost all cases, this causes a reduction in the density of the fluid. So a growing crystal is usually surrounded by a rising convection current. Chen et al.⁹ have demonstrated this in a recent paper. Janssen-van Rosmalen et al.¹⁰ have demonstrated the influence of hydrodynamic environment on the growth and formation of liquid inclusions in large KDP crystals grown by solution technique. It was proposed that veils of liquid inclusions are not a result of starvation in the laminar boundary layer, as suggested earlier, but of depletion in the closed wake at the rear. Growing crystals from a fluid phase under normal gravity conditions involves coupling of the gravitational field with density variations in the fluid, resulting in the generation of convection currents. The spatial and temporal density variations in the fluid media are due to thermal and solutal variations.

Nearly all crystal growth processes involve both a solid and a fluid component. Since internal binding forces in solids are much larger than 1-g forces, only the properties of the fluid are expected to be significantly influenced by gravity. In the liquid state, intrinsic forces such as cohesion or surface tension are of the same order as 1-g forces, and the familiar properties of liquids are the result of the interaction of intermolecular forces and the gravitational forces. If the gravitational forces are reduced considerably, the behavior of fluids will be determined by molecular forces alone. Thus, the environment of the orbital space-lab will have significant influence on the fluid behavior which is expected to affect the crystal growth process. In the absence of convection, diffusion will be much more significant for the mass transport process.

The process of crystallization from solutions represents a typical phase transition in a condensed system. This process is influenced by the creation and structure of the supersaturated solution. The proper crystal growth on the seed inserted into a supersaturated solution is influenced by various factors.

- (a) the degree of supersaturation, which determines the rate and also the mechanism of growth.
- (b) the hydrodynamic conditions in the solution, specially at higher degrees of supersaturation, which influences the transfer of the material from the solution to the crystal through the diffusion layer.
- (c) the temperature of crystallization.
- (d) the quality of the seed used and the chemical purity of the solution.
- (e) Another problem in the growth of large, high-quality single crystals is the strain induced during growth by the method used in holding the original seed. This is specially evident in solution crystal growth where strain induces optical inhomogeneities, cracks and regions of non-uniform growth rates. Recently, Loiacono et al.¹¹ have used a cylindrical seed method to the solution growth of large single crystals of TGS. The method permits the strain-free mounting of oriented seed crystals.
- (f) finally even the manipulation with the crystal as grown (taking the crystal out of equipment, etc.) can strongly influence its properties.

To investigate the crystallization conditions of TGS in view of growing environment, a crystallizer is required which can be used for growing crystals in absence or with a minimum mechanical disturbance in the growing solution.

Growth of crystals on earth is always accompanied by gravity-driven convection currents as well as diffusion fronts.

IV. 2. Effect of Impurity Adsorption on Kinetics of Crystal Growth From Solution.

12

Recently it has been reported by Davey, that a presence of a third component can often have dramatic effects on the crystal growth kinetics (third component may be an impurity). Adsorption of impurities onto the crystal faces changes the relative surface free energies of the faces and may block sites essential to the incorporation of new solute into the crystal lattice. These effects may result in changes in growth kinetics and, hence, habit modification of the crystalline phase.

From the studies of Davey (loc. cit) it seems worth noting the following points in relation to the mechanism of growth rate reduction by impurity adsorption.

- a) Impurity adsorption results in the blocking of key sites on the crystal surface.
- b) Impurities which bear a structural resemblance to the crystallizing component may be most effective in kink and step sites, while impurities which are structurally dissimilar to the crystallizing component may be limited to ledge sites.

The following requirements of an experimental study may be elucidated.

1. Substantiation of growth mechanism for pure solution.
2. Measurement of growth rate as a function of impurity concentration at a fixed supersaturation.
3. Observation of step systems on faces growing in pure and impure solutions.
4. Measurement of adsorption isotherm of the impurity onto the crystal faces under consideration.
5. The selection of experimental system in which the structural nature of the impurity in solution is known.

The experimental data should then be correlated with different available models of crystal growth in solution.

IV. 3. Uncertainties Regarding Crystal Growth in Low-Gravity Environment

For a detailed study of the crystal growth processes in low-gravity environment, uncertainties about residual, transient and non-buoyant convection present and their effect on impurity distribution and the formation of defects in the crystal must be considered. Another area of uncertainty is caused by our poor understanding of the basic mechanisms of crystallization.¹³⁻¹⁴ Choices between competing theories depend on accurate measurements of growth rate as a function of the adjacent thermal and concentration gradients and on interface kinetics terms. All these measurements, when performed on earth in one-g, are distorted by the effects of convection. Measurement of such data in a fluid in a solution growth experiment will be extremely beneficial to the crystal growth theorists.

Also, the effect of low-frequency g-levels on the crystal quality is a very important parameter. Displacements produced by low-frequency (<10 Hz) g-levels are most harmful to solution crystal growth and must be accounted very carefully.

V. EXPERIMENTAL PROCEDURE*

A low temperature solution growth system for growing TGS was designed and fabricated (fig. 1). The system includes an outside bath 27.5 cm x 27.5 cm x 17.5 cm made out of 0.9 cm plexiglass. The bath is heated with two vertical quartz heaters each of 350 watts. The fluid in the outside bath, which is distilled water, is stirred with two stirrers running at 20 rpm using a.c. synchronous motors. The input to the heaters is controlled using a Fisher proportional temperature controller with an accuracy of $\pm 0.01^{\circ}\text{C}$. The actual accuracy of the bath is measured at present only to $\pm 0.1^{\circ}\text{C}$ using NBS calibrated thermometers. The growth solution is kept in a $10 \times 10 \times 10 \text{ cm}^3$ cell made out of 0.6 cm thick plexiglass. The growth cell is surrounded on all sides (except top) by the outside constant temperature bath. The seed crystal is mounted on a specially designed sting which is inserted in the inner cell at a proper time. Details of the sting are given in fig. 2. A stainless steel tube is encapsulated by a plexiglass tube machined to fit the stainless tube. A narrow outer jacket is left between the plexiglass and the stainless tube. A desired flow of high-purity argon gas can be maintained between this narrow jacket. The desired flow of argon gas is monitored through a flow meter.

*This work was done in conjunction with other NASA Contract NAS 8-32945.

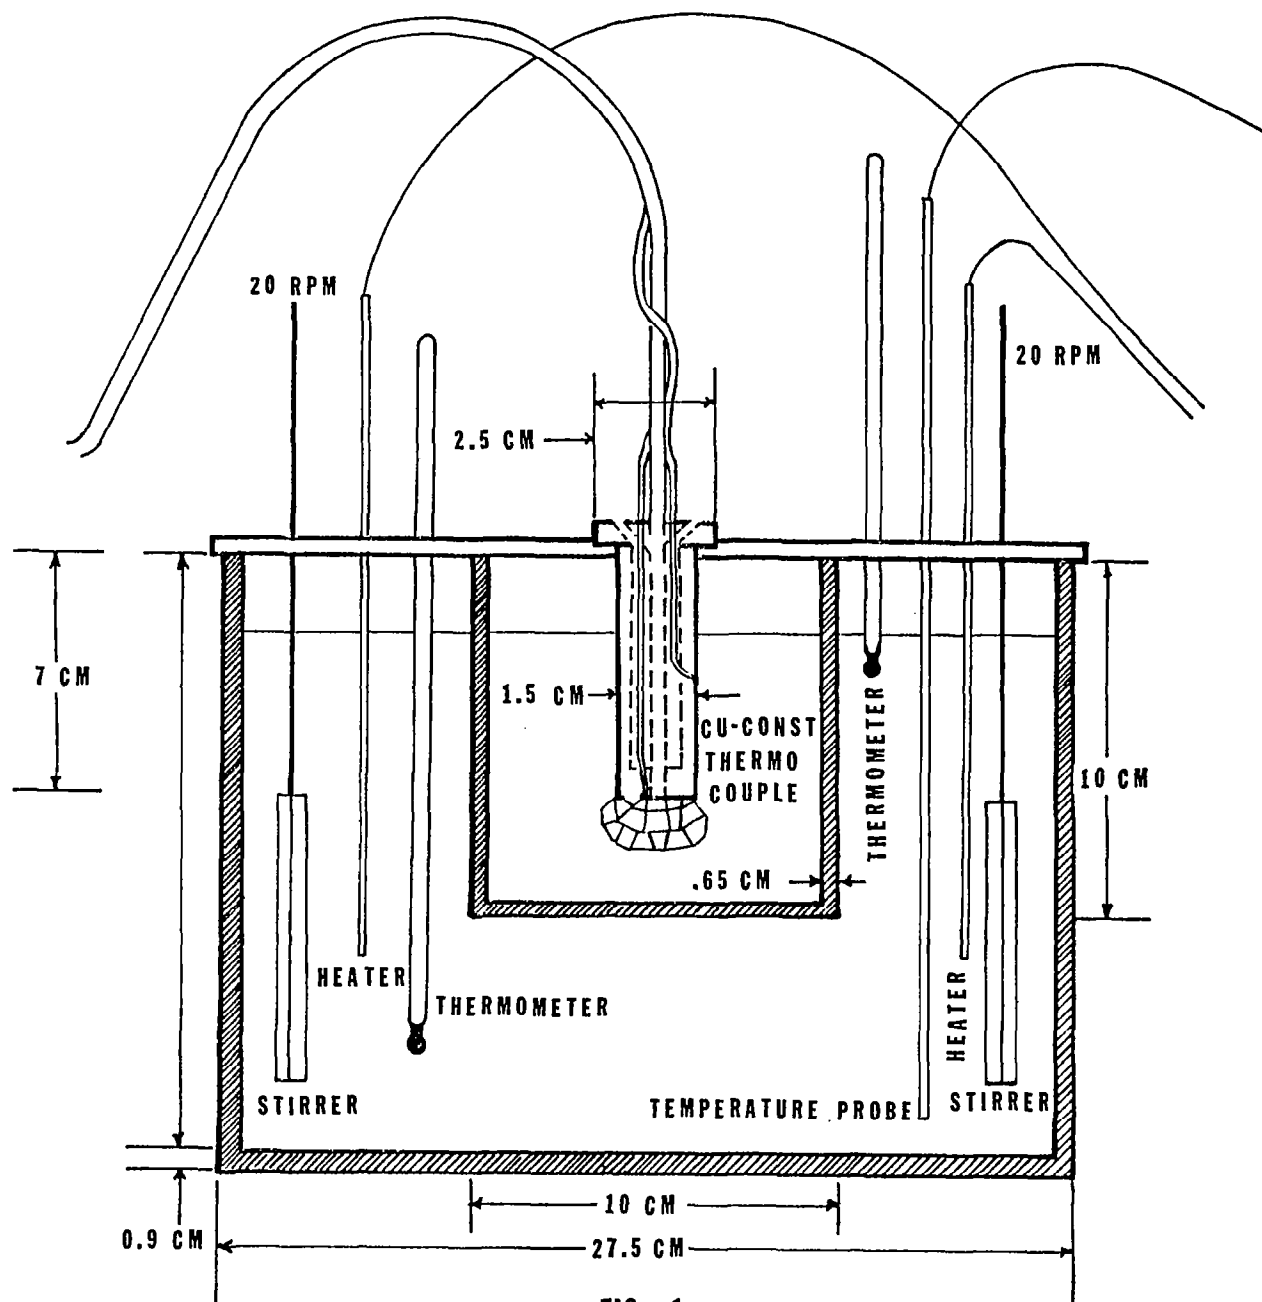


FIG. 1
SOLUTION CRYSTAL GROWTH SYSTEM

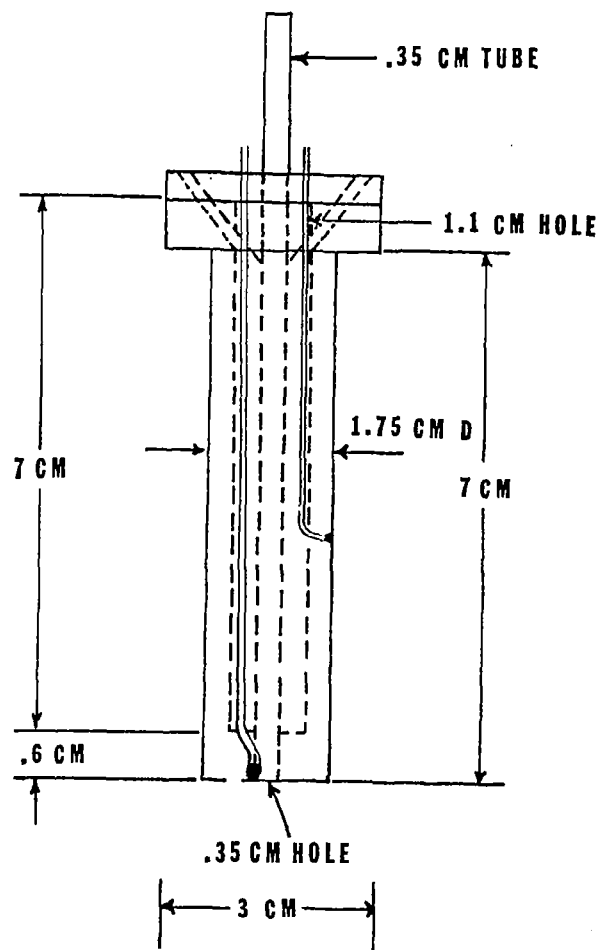


FIG. 2
DESIGN OF STING

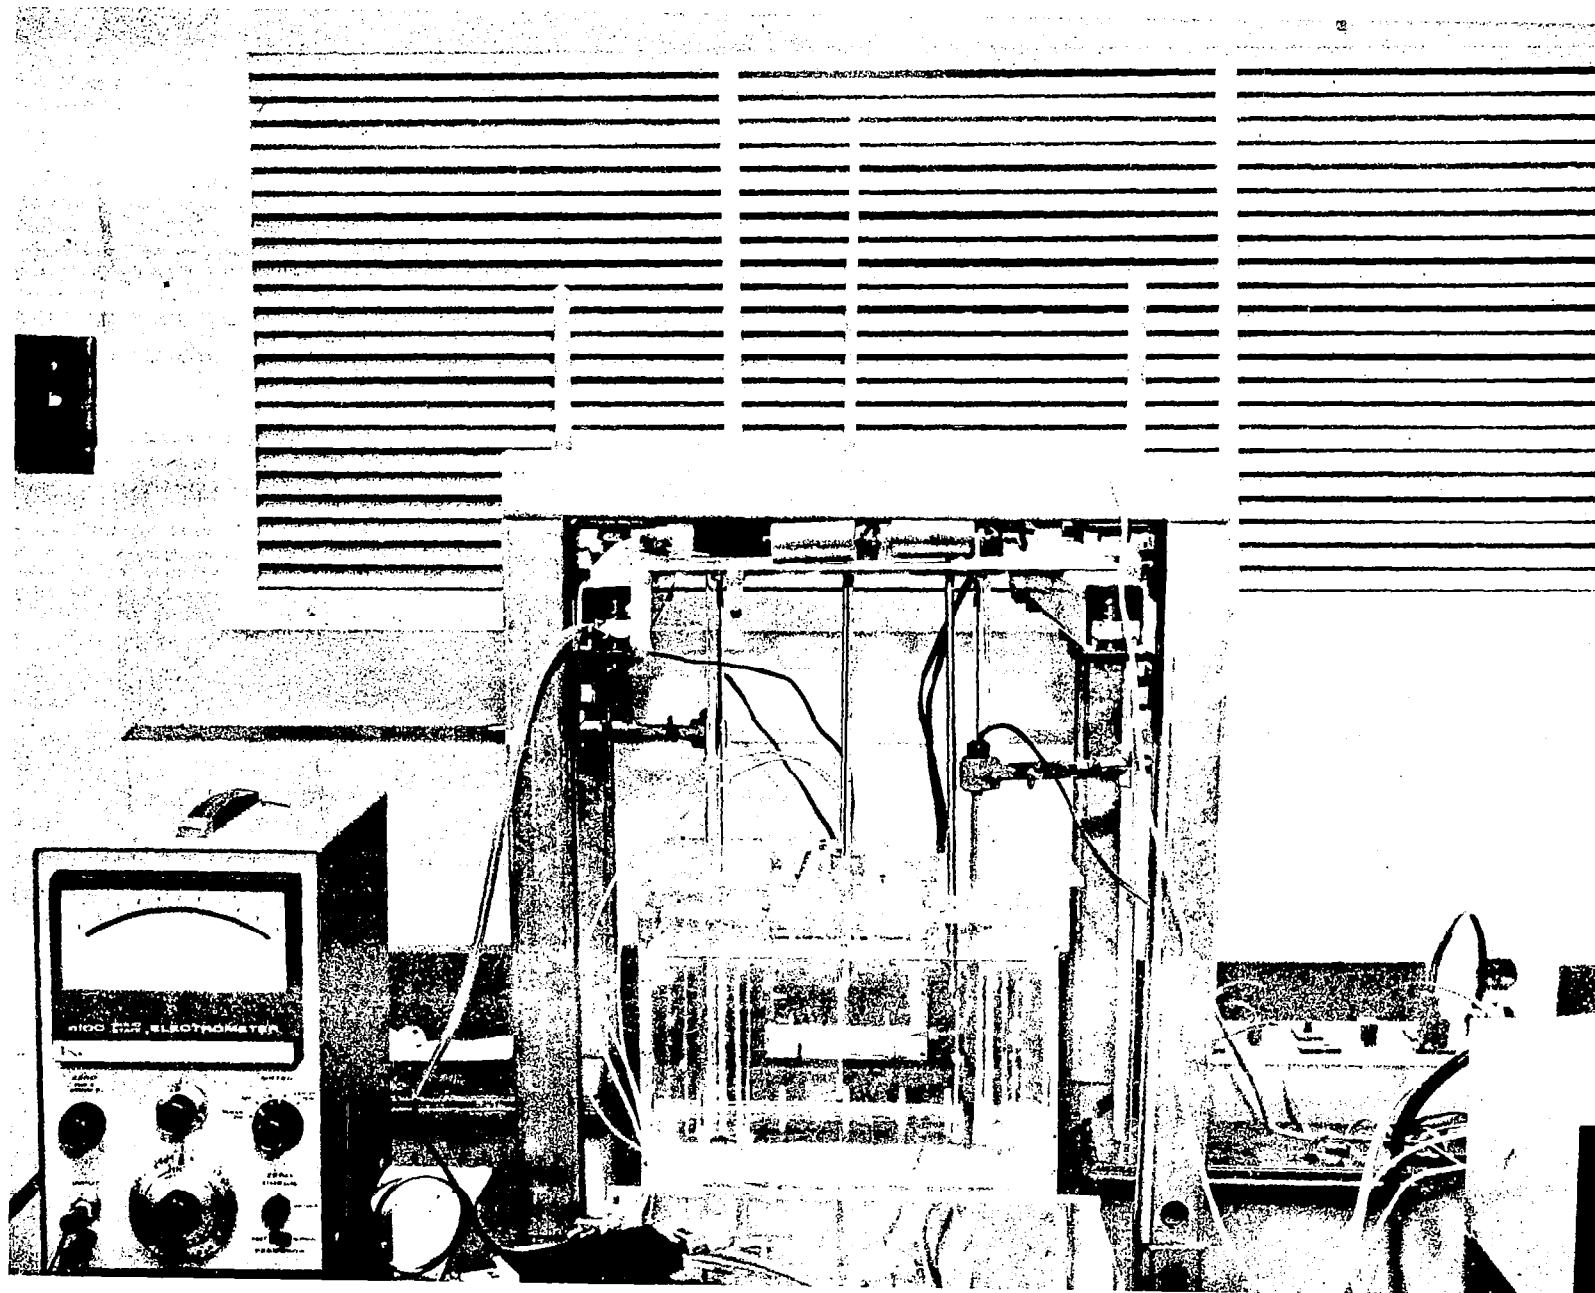


FIG. 3

This serves the purpose of cooling the sting and the seed crystal. The seed crystal is mounted using RTV silicone adhesive at the end of the stainless tube which barely projects out of the plexiglass rod. Two copper-constantan thermocouples have been installed in the sting. One is behind the seed crystal inside the rod and the other on the outside wall of the sting mounted flush to the surface of the sting. The emf of the two thermocouples is measured using a Keithley 610C electrometer. Omega company copper-constantan 0°C temperature compensator is used for 0°C reference junction.

The inner growth cell is tightly covered with a plexiglass cover to avoid any appreciable loss of liquid due to evaporation.

An overall picture of the experimental setup is given in fig.3.

V. 1. Test of Thermal Stability of the System

The thermal stability of the growth system was tested for a desired set temperature (between 30°C - 50°C) over a period of 8-12 hours. The stability of the cell temperature greatly depends upon the stirring provided to the outside bath. In the initial run, commercially available Fisher Scientific stirrers were used. It was found that there was a large variation of temperature ($\pm 4^{\circ}\text{C}$) between the lowest and the top level of the water in the outside bath. The design of the stirrers was modified so that they can stir about 4" of vertical depth of water below the top surface. The bath temperature was then maintained within less than $\pm 0.1^{\circ}\text{C}$ between different layers of water all around the growth cell. The growth cell was also tested for cool-down and heat-up rates. The outside bath can be brought to a desired temperature within $\pm 0.1^{\circ}\text{C}$ in a period of 20 minutes. Due to the poor conduction of plexiglass, the inner cell takes about 2 hours to reach a steady-state temperature, which was found to be 1°C below the outside bath for a particular cell.

V. 2. Growth of TGS Crystals

Initially, seed crystals of TGS were grown by spontaneous nucleation and grown in about 2 or 3% supersaturated solution. Saturated solutions of TGS were prepared from BDH high-purity crystalline Triglycine sulfate using double-distilled water. Solution is filtered at a temperature of a few degrees centigrade above the saturation temperature. At the present time crystal growth experiments have been performed in the ferroelectric range, which is below the transition temperature of TGS ($T_c \approx 49^\circ\text{C}$).

Before the start of the experiment, the outer bath was set at 37°C . The inner cell was filled with 800 ml of 36°C saturated solution of TGS. The pH of the solution was measured as 2.4 ± 0.1 . The cell was left for two hours in the constant temperature bath till its temperature reached a steady value of 36°C . The experiment was initiated by inserting the sting, mounted with a polyhedral seed of TGS using RTV silicone adhesive, in the solution. A slow purge of prepurified Argon at 2 p.s.i. was maintained through the sting. In this initial run no thermocouple was mounted at the tip of the sting so no temperature reading of the tip and the growth solution were recorded during the growth of the crystal. The Argon gas provided a constant cooling of the sting and a constant supersaturation near the seed crystal. The growth process continued for 26 hours. The crystal grew about four times the size of the seed. The total mass deposited in 26 hours was 2.79679 g. This gives an average growth rate of 0.15 mm/hour, but no precise calculation of average mass transfer coefficient (\bar{k}) has been made at this time. This growth rate is appreciably faster than required for a laminar growth. In this growth, an under-cooling of 1°C was maintained on the tip of the sting. At the end

of the experiment the crystal was removed from the growth solution, dried and stored. Due to some inaccuracy in the saturation curve there were some crystallites seen at the bottom of the growth cell.

No evaluation of the grown sample has been done at this time. It is planned that measurement of dielectric constant, specific heat and domain structure studies will be performed. Crystals will be grown at different supersaturation, growth temperatures and by varying the pH of the solution.

V. 3. Evaluation Plan

a) Transition Temperature

The transition temperature T_c can be determined for each sample by plotting the temperature variation of the dielectric constant using a General Radio model 1620-AP capacitance measuring assembly.

b) Domain Structure

The dielectric properties of TGS as defined by the electric permittivity ϵ' and ϵ'' and the spontaneous polarization, P_s , depend strongly on the conditions in which the crystals are grown. Crystals grown above the Curie point at a constant temperature and the ones grown below the Curie point have been found to show different domain structure.¹⁵ Domain structure will be studied in crystals grown in ferroelectric and paraelectric range.

c) Specific Heat Measurements

The relative perfection of ferroelectric crystals can be assessed by the evaluation of the specific heat (C_p) curve in the vicinity of a phase transition. In particular, the width and displacement of C_p curve at the transition is significant. Crystalline defects and/or gross impurities produce internal electrical fields and stresses which can cause broadening of the C_p curve and a reduction of C_p at the transition.¹¹

The specific heat (C_p) for a crystal grown earlier was measured with a Perkin Elmer (DSCI) differential scanning calorimeter.* The measured value of $C_p = 0.3155 \text{ cal/g}^\circ\text{C}$ corresponds to values reported earlier. The precision of the instrument was not adequate to detect any changes in C_p for 0.1°C change in temperature. We are trying to improve the sensitivity of measurements.*

*These measurements were made at the Physics Department of the University of Alabama in Huntsville.

REFERENCES

1. Proceedings of Third Space Processing Symposium, Skylab Results, NASA/MSFC, M-74-5, April (1974).
2. ASTP Review Meeting, NASA/MSFC, Oct. 28-29, (1975).
3. J. C. Brice and P.A.C. Whiffin, Brit. J. Appl. Phys., 18, 581 (1967).
4. B. Cockayne and M. P. Gates, J. Mat. Sci., 2, 118 (1967).
5. K. M. Kim, A. F. Witt, and H. C. Gatos, J. Electrochem. Soc. 119, 1218 (1972).
6. J. T. Yue and F. W. Voltmer, J. Crystal Growth, 29, 329 (1975).
7. H. C. Gatos and A. F. Witt, Final Report NASA Contract, CR-120558, (1974). (Indium Antimonide Crystal Growth experiment M562).
8. J. C. Brice, The growth of crystals from liquids, American Elsevier Publishing Company, Inc., New York (1973).
9. P. S. Chen, P. J. Shlichta, W. R. Wilcox and R. A. Lefever - To be Published J. Crystal Growth.
10. R. Janssen - Van Rosmalen, W. H. Vanderlinden E. Dobbinga and D. Visser, Kristall and Technik, 13, 17 (1978).
11. G. M. Loiacono and W. M. Osborne, J. Crystal Growth, 43, 401 (1978).
12. R. J. Davey, J. Crystal Growth, 34, 109 (1976).
13. M. Ohara and R. C. Reid, Modelling of Crystal Growth rates from Solution, Prentice Hall, Englewood Cliff, NJ (1973).
14. J. R. Bourne and R. J. Davey, J. Crystal Growth, 36, 278, 287 (1976).
15. J. Stankowska and L. Paw Lowcz, Acta. Physica. Polonica, A47, 85 (1975).

BIBLIOGRAPHY

PAPERS ON SOLUTION CRYSTAL GROWTH

- A Simple Method for growing crystals from Solutions A. V. Belyustin;
Sov. Phys. Crystallogr. 10, 651 (1966).
- A Method of Growing Crystals from solution under static conditions.
A. V. Belyustin. N. S. Stepanova. Sov. Phys. Crystallogr. 10, 624,
(1966).
- Occlusion of Mother liquor in solution grown crystals-Richard Brooks,
Avery T. Horton and John L. Torgesen, Journal Crystal Growth 2, 279
(1968).
- Crystallization from solution; factors influencing size distribution.
M. A. Larson, Editor. Chemical engineering progress symposium series.
67, (1971).
- A Crystallizer for the investigation of conditions of growth of single
crystals from solutions. J. Novotry. Kristall and Technik 6, 343 (1971).
- Methode de Croissance en Solution des Monocristaux par L'addition
Graduelle D'un Reactif. I. F. Nicolau, M. Ittu and R. Dabu.
Journal of Crystal Growth 13/14, 462 (1972).
- Equipment from single crystal growth from aqueous solution. John L. Torgesen,
Avery T. Horton and Charles P. Saylor, Journal of Research of The
National Bureau of Standards- Chemical Engineering and Instrumentation.
67c, (1973).
- Crystallization apparatus for the growth of crystals at constant supersaturation
of the solution. A. I. Munchaev. Sov. Phys. Crystallogr. 18, 566 (1974).
- Einfluss von magnetischen und elektromagnetischen Feldern auf die
Kristallisation aus wässrigen Lösungen. C. Barta, L. M. Beljajew,
G. F. Dobrzanski, S. L. Kreinin, M. P. Schaskolskaja, J. Zemlicka,
Kristall and Technik 9, 619 (1974).
- A Crystallizer for growing large single crystals from solution under
Steady-State Concentration Convention Conditions. I. F. Nicolau
Kristall and Technik 9, 1334 (1974).
- P. Bennema, Crystal Growth from solution theory and experiment, J. Cryst,
Growth, 24/25, 76 (1974).
- A. R. Konak, Single versus suspension growth, J. Cryst. Growth, 22, 67 (1974).

PAPERS ON SOLUTION CRYSTAL GROWTH (CONT.)

- Mitsuhiko Hayashi and Takaki Shichiri, Theoretical and experimental study of the growth of perfect crystals, J. Cryst. Growth, 21, 254 (1974).
- A. I. Munchaev, Crystallization apparatus for the growth of crystals at constant supersaturation of the solution, Sov. Phys. Crystallogr, 18, 566 (1974).
- H. Nelson, Liquid Phase Epitaxy - its role in crystal growth technology, J. Cryst. Growth, 27, 1 (1974).
- B. K. Tanner, The Perfection of flux grown crystals, J. Cryst. Growth, 24/25, 637 (1974).
- J. C. Brice, The stability of facets on growing crystals, J. Cryst. Growth, 26, 59 (1974).
- R. L. Moon, The Influence of growth solution thickness on the LPE Layer Thickness and constitutional supercooling requirements for diffusion -- limited growth, J. Cryst. Growth, 27, 62 (1974).
- I. F. Nicolau, A crystallizer for growing large single crystals from solutions under steady-state concentration convention conditions, Kristall and Technik, 9, 1331 (1974).
- G. I. Distler, A. N. Lobacher, Growth of Single Crystals through Interfacial layers, J. Cryst. Growth, 26, 24 (1974).
- H. M. Manasevit, A Survey of Heteroepitaxial growth of Semi-conductor films on insulating substrates, J. Cryst. Growth, 22, 125 (1974).
- Crystal Growth from Solution-Theory and experiment. P. Bennma. Journal Crystal Growth 24/25, 76 (1974).
- Space Processing of Crystals for Opto-electronic devices-The case for solution growth. S. C. Hayden and L. E. Cross. Final Report on Study for Solution Crystal Growth Contract NAS8-31152 10 Sept. 1975.
- Influence of Gravity-Free Solidification on Solute Microsegregation. J. T. Yue and F. W. Voltmer. J. Crystal Growth 29, 329 (1975).
- George E. Moore, Sr., et. al., Worldwide wafers standardization facts or fancy, Solid State Tech., 40 (Feb. 1975).
- John Lenzing, Survey of Semi-conductor crystal growing processes and equipment, Solid State Tech., 34 (1975).
- R. J. Kirkpatrick, Crystal growth from melt! A Review, American Mineralogist, 60, 798 (1975).

Papers on Solution Crystal Growth (cont.)

- P. Bennena and C. Van Leeuwen, Crystal Growth from vapour phase, Confrontation of Theory with experiment, J. Cryst. Growth, 31, 3 (1975).
- G. K. Steel and M. J. Hill, Analysis of the transfer function governing crystal growth in the czochralski process, J. Cryst. Growth, 30, 45 (1975).
- R. Janseen van Rosmalen P. Bennena and J. Garside, The Influence of volume diffusion on crystal growth, J. Cryst. Growth, 29, 342 (1975).
- J. Garside, R. Janseen van Rosmalen and P. Bennena, Verification of Crystal Growth rate equations, J. Cryst. Growth, 29, 353 (1975).
- V. R. Phillips and J. W. Mullin, A technique for observing growth layers and adjacent faces of crystal growing in solution, J. Cryst. Growth, 29, 352 (1975).
- J. C. Brice, J. M. Robertson and J. Vander Heide, A new method of stirring for LPE growth, J. Cryst. Growth, 30 375 (1975).
- R. C. DeMattei, R. A. Huggins and R. S. Feigelson, Crystal Growth by the Electrochemical Czochralski Technique (ECT), J. Cryst. Growth, 34, 1 (1976).
- J. R. Davey, The effect of impurity absorption on the Kinetics of crystal growth from solutions, J. Cryst. Growth, 34, 109 (1976).
- George D. Stareev, A new method for liquid-phase epitaxy, J. Crystal Growth, 32, 189 (1976).
- Influence of the Supersaturation on the mode of thin film growth. I. Markov, R. Kaischew. Kristall and Technik 11, 685 (1976).
- The Effect of Impurity Absorption on the Kinetics of Crystal Growth from Solution. R. J. Davey. J. Crystal Growth 34, 109 (1976).
- Crystal Growth by The Electro Chemical Czochralski Technique (ECT)
R. C. Demattei, R. A. Huggins and R. S. Feigleson, J. Crystal Growth 34, 1 (1976).
- Crystal Growth by Electrolytic Concentration L. M. Rouse and E. A. D. White. J. Crystal Growth 34, 173 (1976).
- Determination of Linear Growth Rates of Crystal (I) Calculation of Linear Growth Rates of Individual Crystal Faces from Overall Rates. Kristall and Technik 11, 149 (1976).
- Determination of Linear Growth Rates of Crystals (II) The Shape Factors Method. J. Nyvlt, Marie Matuchova. Kristall and Technik 11, 245 (1976).

Papers on Solution Crystal Growth (cont.)

- J. R. Carruthers, Origin of Convective temperature oscillations in crystal growth from melt, J. Cryst. Growth, 32, 13 (1976).
- K. Kawamma and Tatsuo Yamamoto, New Apparatus for multilayer liquid-phase epitaxy, J. Cryst. Growth, 32, 157 (1976).
- T. Surrek, Theory of Shaped Stability in crystal growth from the melt, J. Appl. Phys., 47, #10, 4384 (1976).
- New Empirical Kinetic Equation of Size Dependent Crystal Growth and its use. Z. Rojkowski. Kristall and Technik 12 1121 (1977).
- Growth from the vapour by Surface Nucleation. L. M. Rouse. Kristall Technik. 12, 531 (1977).
- An Unusual Type of Epitaxial Growth. A. Hadni, R. Thomas and C. Erhard. Phys. Stat. Sol. (a) 39 419 (1977).
- Growth of Epitaxial layers from a limited volume of melt-solution. A. A. Litvin and I. E. Marochuk. Sov. Phys. Crystallogr. 22, 242 (1977).
- Physiochemical aspects of the hydrothermal growth of crystals. I. C. Ganeev and V. N. Rumyantsev. Sov. Phys. Crystallogr. 22, 91 (1977).
- A phenomenological Analysis of Crystal Growth from Solutions as an Irreversible Process. Tomoya Ogawa. Jap. J. Appl. Phys. 16, 689 (1977).
- The Weighing Method of Automatic Czochralski Crystal Growth. II Control Equipment. W. Bandsley, D. T. J. Hurle, G. C. Joyce and G. C. Wilson. J. Crystal Growth 40, 21 (1977).
- Simple Pressure Chamber for Liquid Encapsulate Czochralski Crystal Growth. E. Buehler, J. Crystal Growth 43, 584 (1978).
- Computational Simulation of the Melt flow During Czochralski Growth. N. Kobnyashi. J. Crystal. Growth 43, 357 (1978).
- A New Technique for Determining The Kinetics of Crystal Growth from the Melt. S. Pech and M. Vignes-Adler. J. Crystal Growth 43, 123 (1978).
- Condition for Constant Growth Rate by LPE from a cooling, static solution. M. B. Small and R. Ghez. J. Crystal Growth 43, 512 (1978).
- A Crystallizer for growing single crystals from a solution, with precise temperature control. J. Mastner and J. Janta. Czech. J. Phys. B20, 230 (1978).
- Evaluation of supersaturation in Crystal Growth from Solution, P. T. Cardew, and R. J. Davey, J. Crystal Growth, 46, 534 (1979).

Papers on Solution Crystal Growth (cont.)

Thermodynamic Driving Force for Crystallization from Solution, O. Sohnel,
J. Crystal Growth, 46, 238 (1979).

Crystallization of Salts from Supersaturated Solutions: Diffusion Kinetics,
I. V. Meliklov, and L. B. Berliner, J. Crystal Growth, 46, 79 (1979).

On the driving force for crystallization, the growth activity, C. Van Leeuwen,
J. Crystal Growth, 46, 91 (1979).

On the presentation of growth curves for growth from solution, C. Van Leeuwen,
J. Crystal Growth, 46, 96 (1979).

PAPERS ON TGS

The Thermodynamic Theory of Ferroelectric Semi-Conducting Solid Solutions.
V. E. Yurkevich and B. N. Rolov; Ferroelectric 6, 67 (1973).

X-Ray Damage on TGS: A Thermodynamic Theory. C. Alemany, J. Mendiola,
B. Jimenz and E. Maurer, Ferroelectrics 5, 11 (1973).

Incident Electron Energy effect on the Ferroelectric Properties of TGS.
Cz. Pawlaczyk and B. Hilczer; Ferroelectrics 6, 33 (1973).

Evaluation of Domain wall thickness in TGS crystals from Thermal Diffusivity
Measurements. T. Krajewski and F. Jaroszyk; Acta Phys. Polon. A43,
845 (1973).

Effect of Growth Conditions on The Thermal Diffusivity and Thermal Conductivity
of TGS Crystals. T. Krajewski and F. Jaroszyk Acta Phys. Polon. A43,
831 (1973).

Effect of Growth Conditions on the Domain Structure of Triglycine Sulphate
Crystals. J. Stankowska and E. Czosnowska, Acta Phys. Polon. A43, 641
(1973).

Characterization of Fully Deuterated Triglycine Sulphate $(ND_2CD_2COOD)_3D_2SO_4$.
H. P. Beerman, Ferroelectrics 8, 653 (1974).

The Influence of The Loss of TGS-Fragments in Ultra-high-Vacuum on The
Spontaneous Polarization and The Coercive Field Strength. V. Ziebert;
Ferroelectrics 8, 645 (1974).

Unipolar FEatures in Strong electric fields of TGS crystals and of The Rochelle
Salt Crystals Doped with Cu^{2+} . J. Eisner; Ferroelectric 8, 621 (1974).

Internal Field in Ferroelectric Triglycine Sulphate Crystals as Studied by
EPR of VO^{2+} Impurities. M. Fujimoto and L. A. Dressel; Ferroelectrics 8,
611 (1974).

Evaluation of the free energy expansion coefficient in TGS. J. Z. Zerem and
A. Halperin, Ferroelectrics 7, 205 (1974).

Change in the permittivity, The Dielectric loss and the Resistance of TGS
caused by the loss of TGS-Fragments in Ultra-High-Vacuum. H. Schmitt
and V. Ziebert; Ferroelectrics 6, 151 (1974).

Dielectric Properties of TGS and TGFB Monocrystals under high pressure.
J. Stankowski, A. Galezewski, S. Wapłak, U. Gruszczynska and H. Gierszal;
Ferroelectrics 6, 209 (1974).

Papers on TGS (cont.)

Alanine Doped TGS/TGSE Crystals for pyroelectric applications.

K. L. Bye, P. W. Whipps, E. T. Keve, and M. R. Josey; *Ferroelectrics* 7, 179 (1974).

Vapour Pressure of Triglycine Sulphate (TGS) Below 130°C. V. Ziebert., *Ferroelectrics* 6, 157 (1974).

Forward Velocity of Domain Walls in the switching of TGS. V. Lopez Rodriguez and J. Gonzalez 1 Beas. *Ferroelectrics* 6, 203 (1973).

Growing of TGS and TGSE Single Crystals at various pH of solution, M. S. Tsedrik, V. N. Ulasen, G. A. Zaborovski., *Kristall and Technik* 10, 49 (1975).

Domain Structure and Dielectric Properties of TGS and DTGS Single Crystals Depending on Growth Conditions. M. S. Tsedrik, G. A. Zaborovski, N. P. Demidorich, L. N. Margolin., *Kristall and Technik* 10, 55 (1975).

Effect of X-Ray Irradiation on The Dielectric Properties & Optical Absorption of Triglycine Sulphate Single Crystals. S. Govinda & K. V. Rao., *Indian J. Pure & Appl. Phys.* 13, 175 (1975).

Growth of Triglycine Sulphate Crystals from Aqueous Solution on Cleaved (010) Surfaces. R. J. Davey and E. A. D. White., *Journal Crystal Growth* 30, 125 (1975).

Influence of Growth Temperature on The Dielectric Properties of Triglycine Sulphate (TGS) Crystals. J. Stankowska and L. Pawlowicz *Acta Phys. Polon.* A47, 85 (1975).

Critical Behavior and Internal Bias of TGS and Isomorphous Crystals Depending on growth conditions. M. S. Tsedrik, G. A. Zaborovski, *Kristall and Technik* 11, 373 (1976).

The Growth of Large Area, Uniformly Doped TGS Crystals. E. A. D. White, J. D. C. Wood and V. M. Wood. *Journal Crystal Growth* 32, 149 (1976).

Physical Properties of Ferroelectrics in the Curie Point Region. B. A. Strukov. *Ferroelectrics* 12, 97 (1976).

Recent Structural Studies of the $\text{KH}_2\text{PO}_4\text{KD}_2\text{PO}_4$ System. N. S. J. Kennedy, R. J. Nemes and F. R. Thornley and K. D. Rouse., *Ferroelectrics* 14, 591 (1976).

Structural Studies of TGS. Part II: After X-Irradiation/Field Treatment (Structure B) S. R. Fletcher, E. T. Keve and A. C. Skapski., *Ferroelectrics*, 14, 789 (1976).

Papers on TGS (cont.)

- Depolarization effects in this ferroelectric films. P. Wurfel and I. P. Batra., *Ferroelectrics*, 12 55 (1976).
- Structural Studies of Triglycine Sulphate Part I: Low Radiation Dose (Structure A) S. R. Fletcher, E. T. Keve and A. C. Skapski., *Ferroelectrics* 14, 775 (1976).
- Microwave Dielectric Dispersion in Triglycine Sulphate, Abhai Mansingh, S. S. Bawa & Gulshan Rai., *Indian J. Pure & Appl. Phys.* 14, 298 (1976).
- Growth of Large Area, Uniformly Doped TGS Crystals. E. A. D. White, J. D. C. Wood and V. M. Wood., *Journal Crystal Growth* 32, 149 (1976).
- Growth Investigations of Single Crystal Sulphates Containing Molecular glycine groups. L. Szezepanska. *Kristall and Technik* 11, 265 (1976).
- Growth of Ferroelectric Triglycine Sulphate Single Crystals. K. N. Srivastava and Bachchan singh., *Indian J. Pure Appl. Phys.* 14, 146 (1976).
- Homogeneity of Triglycine Sulphate Crystals. E. A. D. White, V. M. Wood., *Journal of Materials Science* 11, 612 (1976).
- Observation of Domain Wall Motions in Alanine Doped Triglycine Sulphate Ferroelectric Crystal. Armand Hadni and Robert Thomas. *Appl. Phys.* 10, 91 (1976).
- Triglycine Sulphate Single Crystals Growing Doped with Copper and Colbalt Ions and Study of their Dielectric properties. M. S. Tsedrik, E. M. Kravchenya. *Kristall and Technik* 11, 49 (1976).
- Effects of deuteration and external factors on grain-boundary relaxation in TGS Crystals E. V. Peshikov. *Sov. Phys. Crystallogr.* 20, 743 (1976).
- Spontaneous polarization in thin TGS Single Crystals. N. D. Gavrilova, V. S. Deriglazov, V. A. Koptsik, V. K. Norik, V. G. Poshin and B. V. Selyuk. *Sov. Phys. Crystallogr* 20, 700 (1976).
- Growth of TGS Crystals in the form of Oriented block and a study of their domain structure. V. P. Konstantinova and N. G. Maksimova. *Sov. Phys. Crystallogr.* 22, 127 (1977).
- Crystallization Par Germination Epitaxique. Armand Hadni, Robert Thomas et Christian Erhard. *Journal Crystal Growth* 37, 194 (1977).
- Tellurium Thin-Film Field-Effect Transistor Deposited on TGS Crystal. Yoshizumi Yasuoka, Housuke Hirayama and Toyo-o Miyata., *Jap. J. Appl. Phys.* 16, 1195 (1977).

Papers on TGS (cont.)

On the slope of Growing Pyramids. Christo N. Nanev., Kristall and Technik 12, 587 (1977).

The Physical Properties of TGS Single Crystals, Grown from Aqueous TGS Solutions Containing Aniline. J. Eisner. Phys. Stat. Sol. (a) 43, K1 (1977).

Reversal of Polarization in triglycine sulphate crystals and the dependence of this process on defects already existing in the crystals. N. S. Komlyakova, A. B. Lirhov, Z. Malek, V. M. Rudyak, and L. A. Shuvalov. Sov. Phys. Crystallogr 22, 323 (1977).

Production of Large Area, Doped and Undoped TGS Crystals by Rotating Disc Method. B. J. Lillicrap and J. D. C. Wood. Journal Crystal Growth 41, 205 (1977).

On The Thermodynamic Formalism for adsorbed Layers in Crystal Growth from solution. H. E. Lundager Madsen. Journal Crystal Growth 39, 250 (1977).

The Physical Properties of TGS Single Crystals, Grown from Aqueous TGS Solution containing aniline. J. Eisner. Phys. Stat. Sol. (a) 43, K1 (1977).

An unusual type of Epitaxial Growth A. Hadni, R. Thomas, C. Erhard. Phys. Stat. Sol. (a) 39, 419 (1977).

Crystal Growth from Solution using cylindrical seeds. G. M. Loiacono and W. N. Osborne. J. Crystal Growth 43, 401 (1978).

The Influence of the hydrodynamic Environment on the Growth and the formation of Liquid Inclusions in large KDP Crystals. R. Janssen-Van Rosmalen, V. H. Van Der Linden E. Dobbinga, V. Visser. Kristall and Technik 13, 17 (1978).

1. REPORT NO. NASA CR-3370		2. GOVERNMENT ACCESSION NO.		3. RECIPIENT'S CATALOG NO.	
4. TITLE AND SUBTITLE A Study of Crystal Growth by Solution Technique				5. REPORT DATE January 1981	
				6. PERFORMING ORGANIZATION CODE	
7. AUTHOR(S) R. B. Lal				8. PERFORMING ORGANIZATION REPORT #	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Physics Alabama Agriculture and Mechanical University Huntsville, Alabama 35762				10. WORK UNIT, NO. M-318	
				11. CONTRACT OR GRANT NO. NSG-8033	
12. SPONSORING AGENCY NAME AND ADDRESS National Aeronautics and Space Administration Washington, D. C. 20546				13. TYPE OF REPORT & PERIOD COVERED Contractor Report	
				14. SPONSORING AGENCY CODE	
15. SUPPLEMENTARY NOTES Marshall Technical Monitor: Charles Schafer Final Report					
16. ABSTRACT The purpose of this investigation is to study the mechanism of crystal growth by solution technique. A low-temperature solution crystal growth setup is developed. Crystals of Triglycine Sulfate (TGS) are grown using this arrangement. Some additional tasks were performed toward fabrication of some experiments for future space flights.					
17. KEY WORDS Crystal growth Solution crystal growth Spacelab 3 mission			18. DISTRIBUTION STATEMENT Unclassified - Unlimited Subject Category 76		
19. SECURITY CLASSIF. (of this report) Unclassified	20. SECURITY CLASSIF. (of this page) Unclassified	21. NO. OF PAGES 33	22. PRICE A02		